

This article was downloaded by:

On: 20 January 2011

Access details: *Access Details: Free Access*

Publisher *Taylor & Francis*

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



## Molecular Crystals and Liquid Crystals

Publication details, including instructions for authors and subscription information:

<http://www.informaworld.com/smpp/title~content=t713644168>

## Paramagnetic Nematic Liquid Crystals

S. Chandrasekhar<sup>a</sup>; B. K. Sadashiva<sup>a</sup>; B. S. Srikanta<sup>a</sup>

<sup>a</sup> Raman Research Institute, Bangalore, India

First published on: 01 October 1987

**To cite this Article** Chandrasekhar, S. , Sadashiva, B. K. and Srikanta, B. S.(1987) 'Paramagnetic Nematic Liquid Crystals', *Molecular Crystals and Liquid Crystals*, 151: 1, 93 – 107

**To link to this Article:** DOI: 10.1080/00268948708075322

**URL:** <http://dx.doi.org/10.1080/00268948708075322>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.informaworld.com/terms-and-conditions-of-access.pdf>

This article may be used for research, teaching and private study purposes. Any substantial or systematic reproduction, re-distribution, re-selling, loan or sub-licensing, systematic supply or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

## Paramagnetic Nematic Liquid Crystals

S. CHANDRASEKHAR, B.K.SADASHIVA and B.S.SRIKANTA  
Raman Research Institute, Bangalore 560080, India

**Abstract.** Five nematogenic complexes, bis[1-(p-n-decylbiphenyl)3-(p-substituted phenyl)propane-1,3-dionato]-copper (II), have been prepared. The mesophase, which occurs monotropically in all of them, is of the usual nematic type, but has paramagnetic properties. Magnetic, dielectric and electron paramagnetic resonance measurements are presented. A preliminary analysis of the data indicates the existence of antiparallel correlations in the nematic phase.

### Introduction

In a recent note,<sup>1</sup> we presented examples of new complexes that form paramagnetic nematic liquid crystals. We established by miscibility studies that the mesophases are of the usual nematic type, i.e., composed of rod-like molecules, and by magnetic susceptibility measurements that they are, in fact, paramagnetic. We now describe some further investigations on these materials.

The first copper containing (discotic) mesogens were prepared by Giroud-Godquin and Billard,<sup>2,3</sup> and since then other similar materials have been synthesized,<sup>4-7</sup> but none of them exhibit a nematic phase. We felt that it would be of interest to explore this possibility, and were able to prepare a few nematogenic copper complexes. After these studies had been completed,<sup>1</sup> we came across a report by Galyametdinov et al.<sup>8</sup> on bis(4-heptyloxy-2-hydroxy-N-4-phenyloxy (dodecyloxybenzoate) benzaldimi-

---

Presented at the Fifth European Winter Liquid  
Crystal Conference, Borovets, Bulgaria, March 1987

nato) copper (II). However, as even the transition temperatures of this complex are not given in their report,<sup>8</sup> we shall not discuss their work any further in this paper.

### Experimental

4-n-Decyl-4'-acetylbi phenyl was prepared following the method described by Byron et al.<sup>9</sup> The ligands and the corresponding copper complexes were prepared according to the scheme shown in figure 1. All the complexes were recrystallised several times from methyl ethyl ketone and obtained as green needles. The transition temperatures were determined with a polarizing microscope equipped with a heating stage and a controller (Mettler FP52 and FP5) and from thermograms recorded on a differential scanning calorimeter (Perkin-Elmer, Model DSC2 or DSC4). The calorimeter was calibrated using pure indium as a standard. The enthalpies of transitions were also calculated from the thermograms. The purity was checked by analytical and spectral data. The elemental analysis data are given in table 1. Infrared and electronic absorption spectra were recorded on Shimadzu IR-435 and Hitachi U-3200 spectrophotometers. Typical values for complex 3 of table 2 are -

$$\text{IR } \nu_{\text{max}} \text{ (nujol mull)} \quad 1588 \text{ cm}^{-1} \text{ and } 1608 \text{ cm}^{-1}$$

$$\text{UV-VIS } \lambda_{\text{max}}^{\text{CHCl}_3} (\epsilon) \quad 366 (84,000) \quad 316 (57,000) \text{ and} \\ 240 (51,000).$$

Magnetic susceptibility measurements were made using a Cahn RG balance, which was calibrated with  $\text{Hg}[\text{CO}(\text{SCN})_4]$ . EPR spectra were recorded on a Varian E109 spectrometer operating at X-band frequency (9.05 GHz); the samples were heated using a Varian variable temperature acce-

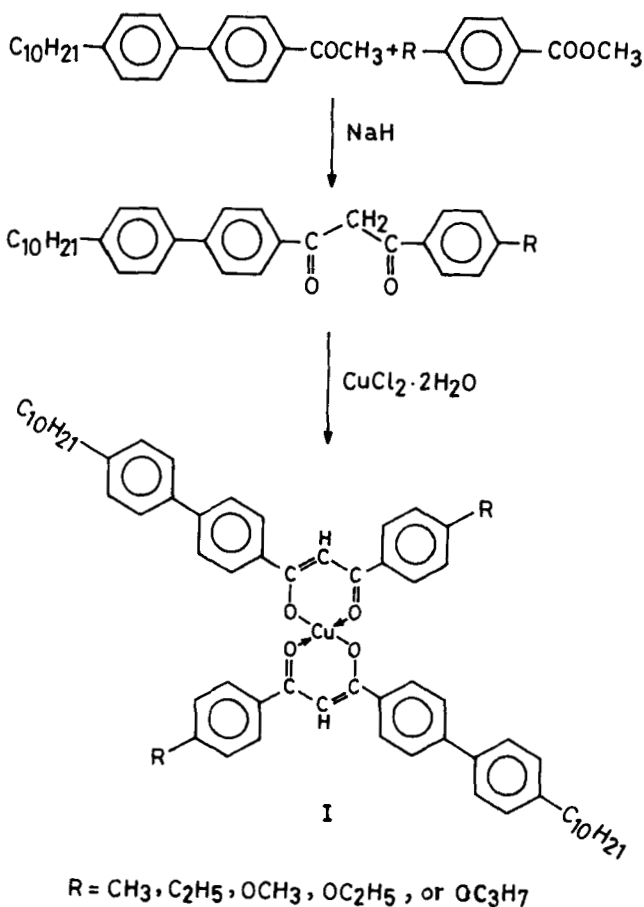


Fig. 1. Synthetic route for bis[1-(p-n-decylbiphenyl) 3-(p-substituted phenyl)propane 1,3-dionato] copper (II) complexes.

Table 1. Elemental analysis data of the complexes I

Complex number	Calculated, %		Found, %	
	C	H	C	H
1	79.22	7.63	79.20	7.54
2	79.39	7.82	79.30	7.82
3	76.68	7.39	76.76	7.39
4	76.93	7.58	76.79	7.49
5	77.16	7.75	77.02	7.65

ssory (E257/WL-257) and the temperature was controlled by nitrogen gas flow. The dielectric constants were measured with a Wayne-Kerr bridge (Model B642) operating at 1592 Hz.

### Thermodynamic data

The temperatures and heats of transition for the five complexes are given in table 2. The transition to the nematic phase is monotropic in all five cases. Complexes 1 and 2 show the nematic phase after considerable supercooling of the isotropic liquid, so that the crystallisation is more or less immediate. Hence

Table 2. Transition temperatures ( $^{\circ}\text{C}$ ) and heats of transition (kcal/mole)

Complex number	R	K	N	I
1	$\text{CH}_3$	.	224.0 12.68	. (169.5) <sup>a</sup> - .
2	$\text{C}_2\text{H}_5$	.	181.5 9.20	. (153.8) <sup>a</sup> - .
3	$\text{OCH}_3$	.	194.0 12.11	. (179.0) 0.092 .
4	$\text{OC}_2\text{H}_5$	.	186.6 12.24	. (166.5) 0.093 .
5	$\text{OC}_3\text{H}_7$	.	183.5 13.66	. (153.5) 0.096 .

K : Crystal, N : Nematic and I : Isotropic liquid

<sup>a</sup>The heat of transition could not be accurately determined because of the onset of crystallisation

The temperature in parentheses indicates a monotropic transition.

the heat of N-I transition ( $\Delta H_{NI}$ ) could not be measured for these two cases. For complexes 3, 4 and 5,  $\Delta H_{NI} = 0.092$ , 0.093 and 0.096 kcal/mole respectively. These values are slightly lower than what is usually observed for this transition.<sup>10</sup> Complex 3 exhibits a metastable nematic phase which exists over an appreciable temperature range before crystallisation occurs. As such a number of physical measurements could be made on this complex.

Structure I (figure 1) can be looked upon as an elongated molecule with two lateral substituents: the two biphenyl moieties with the decyl chains form the long axis, while the two phenyl rings with R form the 'lateral' substituent. Consequently, the mesophases of these complexes may be expected to be of the usual nematic type composed of 'rod-like' molecules. This was confirmed<sup>1</sup> by studying the miscibility of complex 3 with the well known nematogen 4"-n-pentyl-4-cyano-p-terphenyl (5CT). For the sake of completeness, we reproduce the miscibility diagram in figure 2. It was also ascertained that the nematic phases of complexes 3 and 4 are continuously miscible.

### Magnetic susceptibility measurements

The magnetic susceptibilities in the three phases of complex 3, uncorrected for diamagnetism, were found to be:

$$\left. \begin{array}{l} \text{Polycrystal at } 27^{\circ}\text{C} \\ \text{Nematic at } 175^{\circ}\text{C} \\ \text{Isotropic liquid at } 200^{\circ}\text{C} \end{array} \right\} \begin{array}{l} X_{\text{mean}} = 901.4 \\ X_{\text{n}} = 140.2 \\ X_{\text{is}} = 60.1 \end{array} \times 10^{-6} \text{ emu/mole}$$

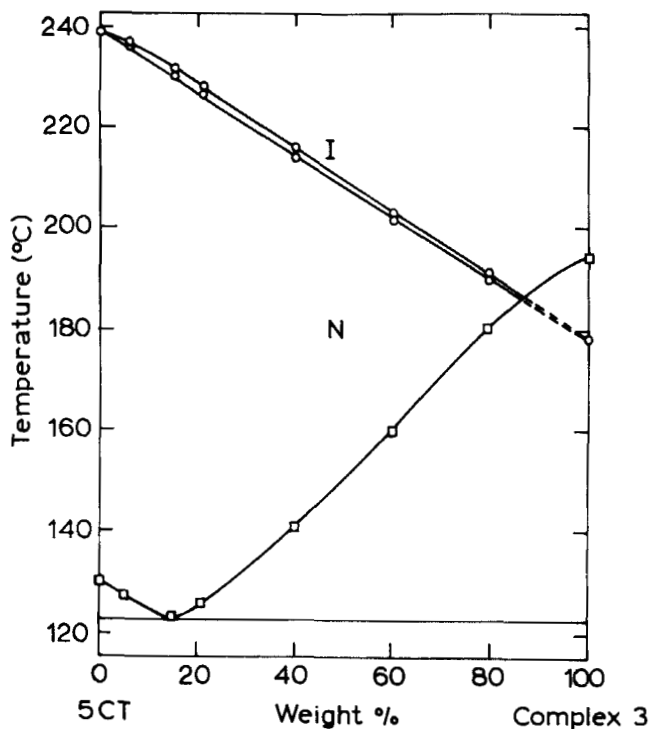


Fig.2. Miscibility diagram of 5CT with complex 3. Squares represent the solid-nematic or solid-isotropic transitions determined in the heating mode, and circles the isotropic-nematic (I-N) transitions determined in the cooling mode. The dashed lines signify monotropic transitions.

It was verified that the anisotropy of magnetic susceptibility in the nematic phase is positive ( $\Delta\chi = \Delta\chi_{\text{para}} + \Delta\chi_{\text{dia}} > 0$ ) by observing the Fredericksz transition in a homeotropically aligned sample (bend geometry); the threshold field was 6.6 kG for a sample of thickness 25  $\mu\text{m}$ . Since the diameter of the sample container of the Cahn RG balance was about 5 mm and the magnetic field

used was 3 kG, it is clear that the measured susceptibility in the nematic phase represents  $\chi_{||}$  for an aligned sample.

$\chi_{||}$  and  $\chi_{is}$  were also determined as functions of temperature. The temperature stability was estimated to be better than  $\pm 0.2^\circ\text{C}$ . The observed molar susceptibility is plotted against T in figure 3.

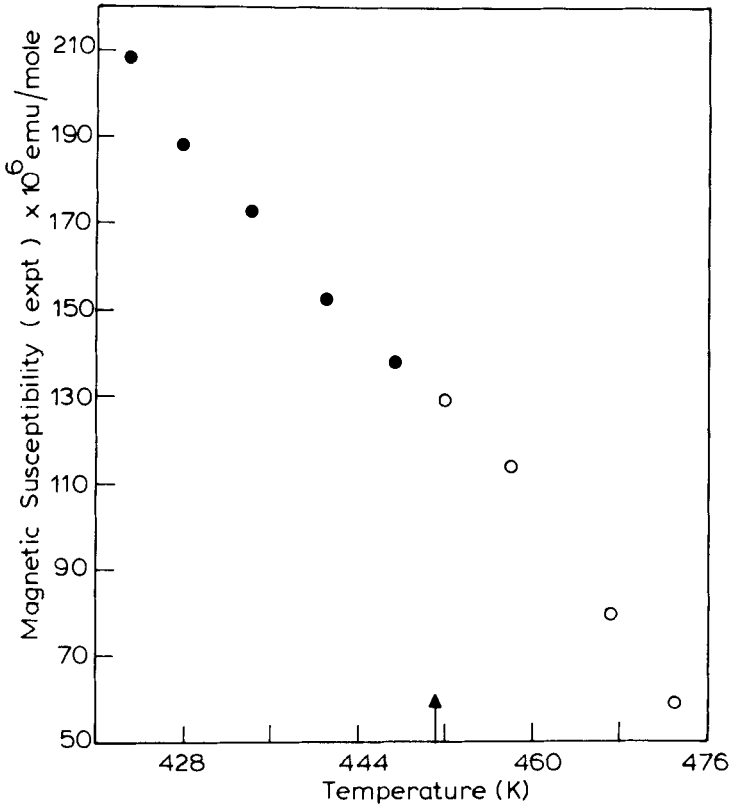


Fig. 3. Experimental values of the magnetic susceptibility (uncorrected for diamagnetism). Open circles represent  $\chi_{isotropic}$  and closed circles  $\chi_{||}$  in the nematic phase. The arrow represents the N-I transition temperature.



$\chi_{is}$  was corrected for diamagnetism by the standard procedure.<sup>11</sup> The diamagnetic anisotropy in the nematic phase was calculated by Flygare's method,<sup>12</sup> which has proved to be quite successful in a number of cases.<sup>13-15</sup> The contribution of the alkyl chains to the anisotropy was taken to be negligible.<sup>13-17</sup> One then gets

$$[\chi_{||}]_{\text{dia}} = \bar{\chi}_{\text{dia}} + \frac{2}{3} S \Delta \chi_{\text{dia}}$$

where  $S$  is the order parameter, which can be obtained from the Maier-Saupe theory. Although the absolute value of  $S$  derived from this theory may be in error, the predicted temperature variation of  $S$  tends to be reasonably accurate (except very close to the transition). As we shall see, it is the temperature variation that is probably more relevant to our discussion. The calculated susceptibilities in the isotropic and nematic phases are given in figure 4; the trend is in agreement with experimental curves for diamagnetic nematics.<sup>17,18</sup>

The paramagnetic susceptibility, after correcting for diamagnetism, versus  $1/T$  is presented in figure 5. There is a Curie-Law type of variation in both phases, but the slope for  $\chi_{is}$  is nearly twice that for  $\chi_{||}$  in the nematic. A plot of  $1/\chi$  versus  $T$  also leads to essentially the same conclusion. The negative paramagnetic anisotropy of the molecule may account for a small part of the difference in the slopes, but even allowing for this, it appears that the effective magnetic moment per molecule is lower in the nematic, perhaps due to antiparallel correlations in this phase. However further studies are necessary before this result can be established conclusively.

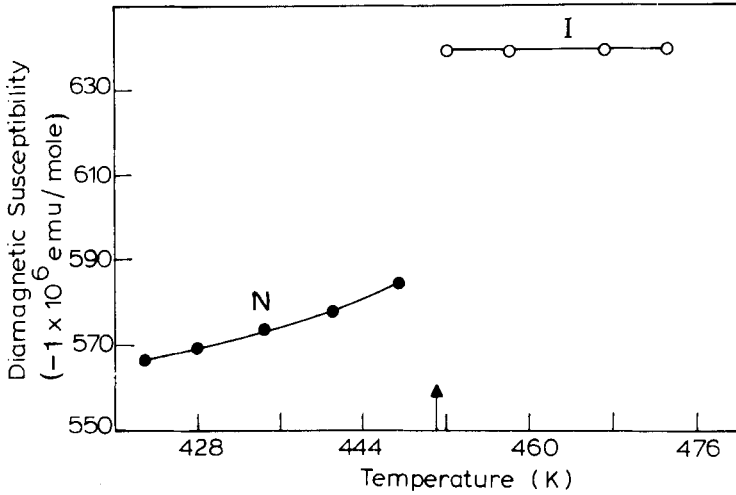


Fig.4. Calculated diamagnetic susceptibility. Open circles represent  $\chi_{isotropic}$  and closed circles  $\chi_{n}$  in the nematic phase.

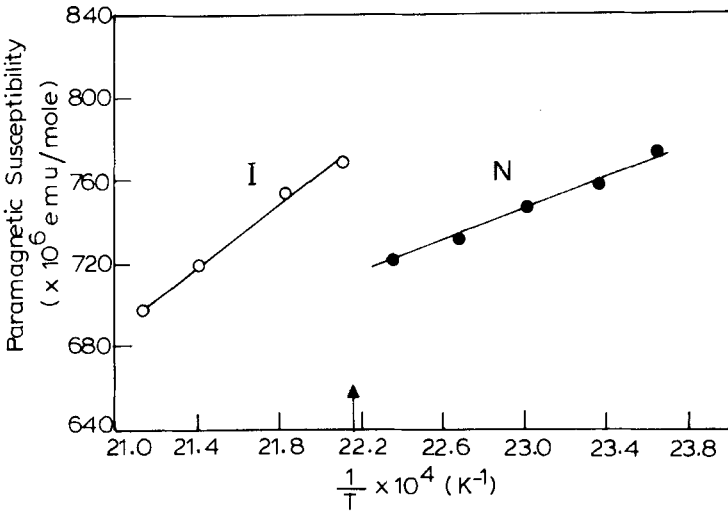


Fig. 5. Paramagnetic susceptibility versus  $1/T$ .

### Electron paramagnetic resonance (EPR) studies

The EPR spectra were recorded in the polycrystalline, nematic and isotropic phases of complexes 3 and 4. Figure 6 gives the spectra for complex 3. The spectra were closely similar for complex 4 and  $g_{\parallel}$  and  $g_{\perp}$  in the nematic phase were calculated to be 2.261 and 2.062 for both complexes. These values agree well with those reported for other copper complexes.<sup>19</sup> (Here  $\parallel$  and  $\perp$  are with reference to the unique axis of the complex.) From the magnitude of the hyperfine spacing, it would seem that the rate of molecular reorientation is slow, i.e., the rotational correlation time is greater than about  $10^{-8}$  s. This implies that the viscosity is high or that there are molecular aggregates or, most probably, a combination of the two. Such aggregates appear to be present in the isotropic phase as well, for the spectra are essentially unchanged at the transition. A more detailed analysis of the data would evidently be of much interest. As we shall see presently, dielectric studies provide supporting evidence for the existence of strong near neighbour correlations.

On the other hand, the spectra of a dilute solution of complex 3 in 5CT (0.13 mole %) were of the standard type for a paramagnetic probe in a nematic.

### Dielectric constant measurements

Dielectric constant measurements were made on complex 3. A 100 micron thick sample was taken between tin oxide coated glass plates and aligned in a 15 kG magnetic field. Both  $\epsilon_{\parallel}$  and  $\epsilon_{\perp}$  were measured on the same sample by rotating the cell to the appropriate configuration.

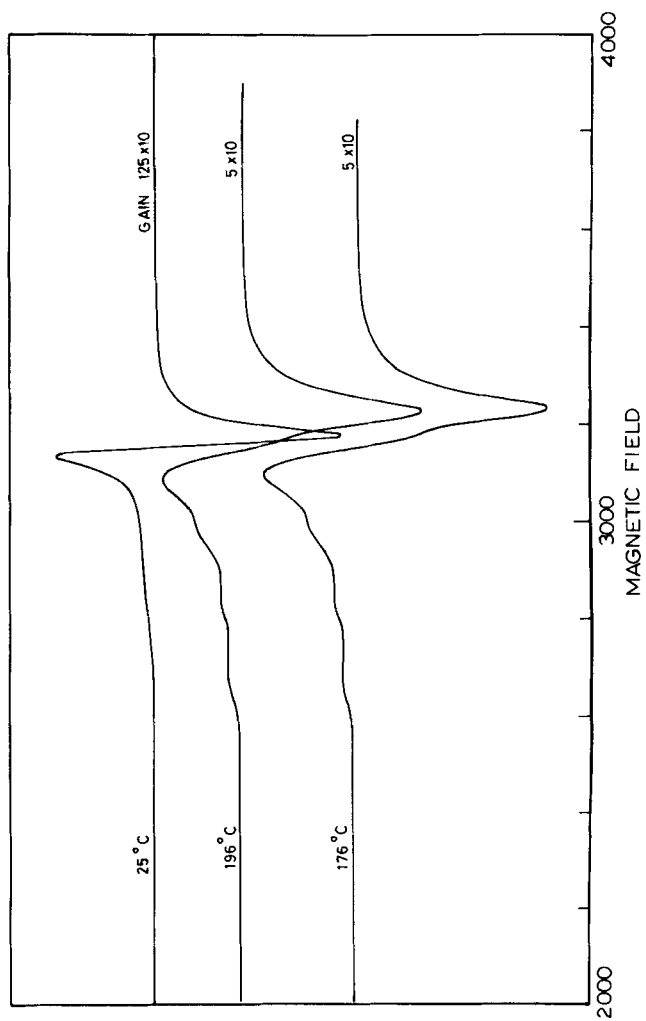


Fig. 6. EPR spectra of complex 3 in the polycrystalline (25°C), isotropic (196°C) and nematic (176°C) phases.

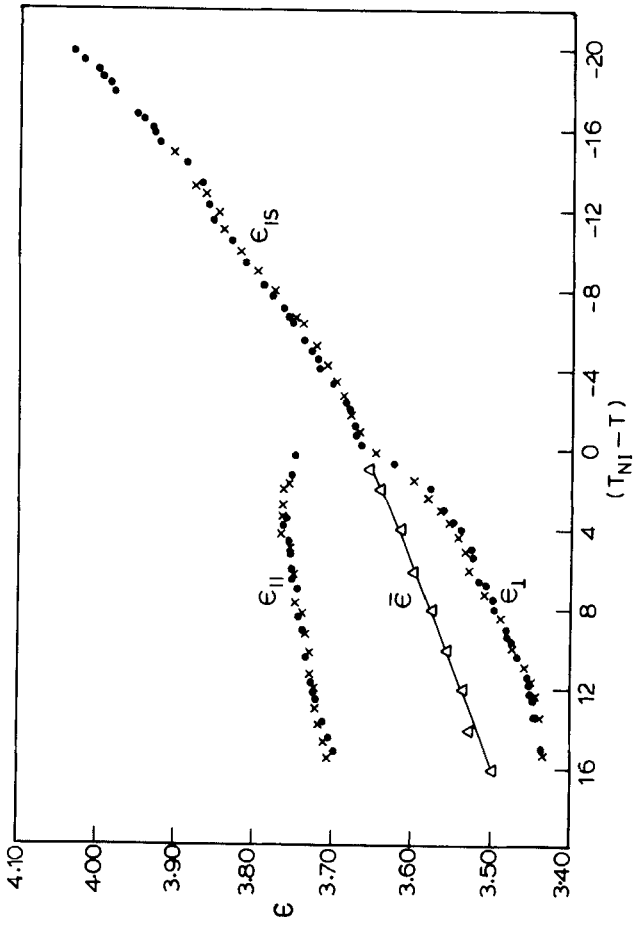


Fig. 7.  $\epsilon_{II}$ ,  $\epsilon_I$ ,  $\epsilon_{IS}$  and  $\bar{\epsilon}$  versus  $T$ . Dots and crosses represent independent sets of measurements on two separate samples.

$\epsilon_{\parallel}$ ,  $\epsilon_{\perp}$ ,  $\bar{\epsilon}$  and  $\epsilon_{is}$  are plotted in figure 7, and the dielectric anisotropy ( $\Delta\epsilon$ ) in figure 8.

The most striking feature about these results is that  $\bar{\epsilon}$  as well as  $\epsilon_{is}$  increase markedly with increase of temperature, indicating a high degree of near neighbour antiparallel correlation.<sup>20</sup> This behaviour is remarkable in view of the fact that the dielectric anisotropy is quite small, only about 0.27 at the lowest temperature of measurement.

The birefringence of the nematic was determined to be 0.18 at  $T_{NI} - T \approx 10^{\circ}$ .

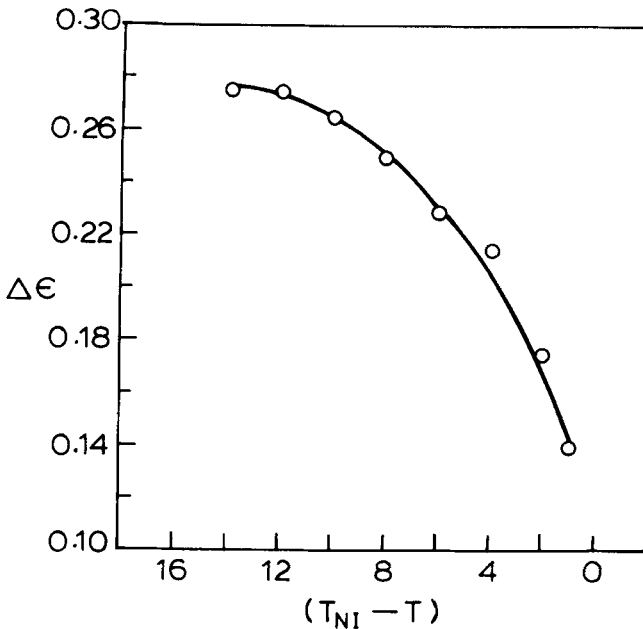


Fig. 8. Temperature variation of the dielectric anisotropy

### Acknowledgements

We are very grateful to Prof. G. R. Luckhurst for his comments on the EPR spectra, to Prof. J. Simon for interesting discussions, and to our colleagues N. V. Madhusudana, G. S. Ranganath, B. R. Ratna and R. Shashidhar for many helpful suggestions. Our thanks are also due to the Solid State and Structural Chemistry Unit, Indian Institute of Science, for allowing us to use the Cahn RG balance and the Varian ESR spectrometer.

### References

- 1 S. Chandrasekhar, B.K.Sadashiva, S.Ramesha and B.S. Srikanta, *Pramana, J. Phys.*, **27(5)**, L713 (1986)
- 2 A.M.Giroud-Godquin and J.Billard, *Mol. Cryst. Liq. Cryst.*, **66**, 147 (1981)
- 3 A.M.Giroud-Godquin and J.Billard, *Mol. Cryst. Liq. Cryst.*, **97**, 287 (1983)
- 4 K.Ohta, A.Ishii, H.Muroki, I.Yamamoto and K.Matsuzaki, *Mol. Cryst. Liq. Cryst.*, **116**, 299 (1985)
- 5 K.Ohta, H.Muroki, A.Takagi, I.Yamamoto and K.Matsuzaki, *Mol. Cryst. Liq. Cryst.*, **135**, 247 (1986)
- 6 K.Ohta, H.Muroki, A.Takagi, K.I.Hatada, H.Ema, I.Yamamoto and K.Matsuzaki, *Mol. Cryst. Liq. Cryst.*, **140**, 131 (1986)
- 7 C.Piechocki, J.Simon, A.Skoulios, D.Guillon and P. Weber, *J. Amer. Chem. Soc.*, **104**, 5245 (1982)
- 8 Yu.G.Galyametdinov, D.Z.Zakieva and I.V.Ovchinnikov, *Izv. Akad. Nauk SSSR, Ser. Khim* (2), 491 (1986)
- 9 D.J.Byron, G.W.Gray and R.C.Wilson, *J. Chem. Soc. (C)*, 840 (1966)
- 10 A.Beguin, J.Billard, F.Bonamy, J.M.Buisine, P.Cuve-lier, J.C.Dubois and P. Le Barny, *Mol. Cryst. Liq. Cryst.*, **115**, (1984)
- 11 *Theory and Applications of Molecular Diamagnetism*, Ed. L.N.Mulay and E.A.Boudreaux (John Wiley, 1976)

- 12 W.H.Flygare, Chem. Rev., **74**, 653 (1974)
- 13 P.L.Sherrell and D.A.Crellin, J. de Physique, **40**, C3-211 (1979)
- 14 F.Leenhouts, H.J.Roebbers, A.J.Dekker and J.J.Jonker, J. de Physique, **40**, C3-291 (1979)
- 15 K.P.L.Moodithaya, Optical and Elastic Properties of Liquid Crystals, Ph. D. Thesis, University of Mysore, 1982; N.V.Madhusudana and R.Pratibha, Mol. Cryst. Liq. Cryst., **89**, 249 (1982)
- 16 D.W.Davies, Mol. Phys., **6**, 489 (1963)
- 17 W.H. de Jeu and W.A.P.Claassen, J. Chem. Phys., **68**, 102 (1978)
- 18 H.Gasparoux, F.Hardouin and M.F.Achard, Proc. Int. Liquid Crystals Conf., Bangalore, December 1973, Pramana, Suppl. 1, 215
- 19 Landolt-Bornstein Numerical Data and Functional Relations in Science and Technology, Group II. Atomic and Molecular Physics, Vol.2, Magnetic properties of coordination and organo-metallic transition metal compounds (Springer-Verlag, 1966)
- 20 N.V.Madhusudana and S.Chandrasekhar, Proc. Int. Liquid Crystals Conf., Bangalore, December 1973, Pramana, Suppl. 1, p. 57.